


**CLOSURE TURF LLC -LANDFILL COVER SYSTEM
RETAINED TENSILE STRENGTH VS. WEATHERING TIME**

Artificial Grass (Green Fibrillated Yarn)
Desert Weathering, New River, Arizona
Direct 45 Deg South, Plywood Backing

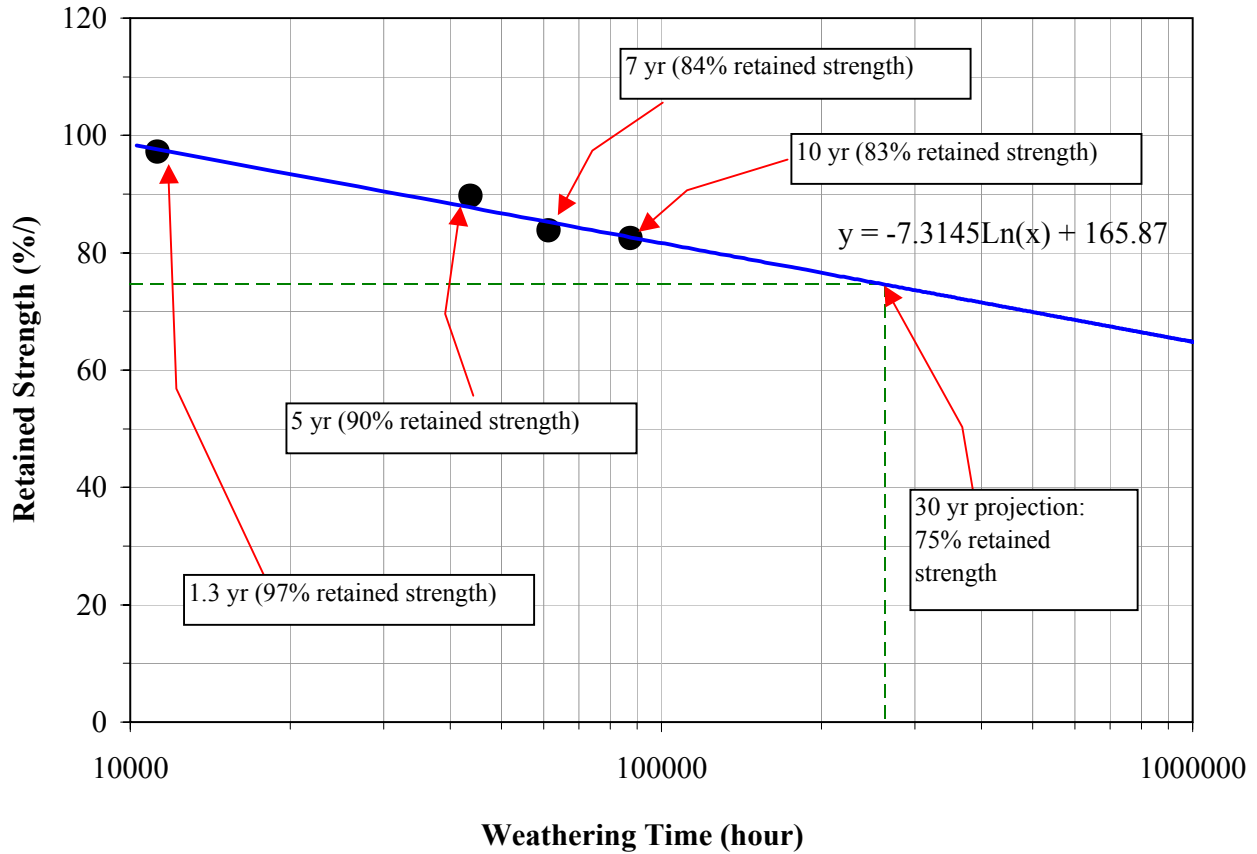

Weathered ClosureTuff™ Sample #1	Test Specimen	Weathering Time		Tensile Strength		Observation (-)
		(year)	(hours)	Control (lbs/in.)	Weathered (%)	
1	Top Portion 2" long Artificial Grass	1.3	11280	25.4	97.2	
2		5.0	43800	20.2	89.7	
3		7.0	61320	20.2	83.8	
4		10.0	87600	20.2	82.5	

Projected Retained Strength at 60 years (%): **70**



SGI TESTING SERVICES, LLC

DATE REPORTED: 9/12/2012

FIGURE NO. 1

PROJECT NO. SGI11030

DOCUMENT NO.

FILE NO.